




## Cite as

Nano-Micro Lett.  
(2023) 15:163Received: 21 April 2023  
Accepted: 22 May 2023  
© The Author(s) 2023In Situ Iodide Passivation Toward Efficient CsPbI<sub>3</sub> Perovskite Quantum Dot Solar CellsJunwei Shi<sup>1,2</sup>, Ben Cohen-Kleinstei<sup>3</sup>, Xuliang Zhang<sup>2</sup>, Chenyu Zhao<sup>2</sup>, Yong Zhang<sup>1</sup>, Xufeng Ling<sup>2</sup>, Junjun Guo<sup>2</sup>, Doo-Hyun Ko<sup>4</sup>, Baomin Xu<sup>1</sup> ✉, Jianyu Yuan<sup>2,5</sup> ✉, Wanli Ma<sup>2,6</sup> ✉

## HIGHLIGHTS

- The introduction of hydroiodic acid (HI) manipulates the dynamic conversion of PbI<sub>2</sub> into highly coordinated species to optimize the nucleation and growth kinetics.
- The addition of HI enables the fabrication of CsPbI<sub>3</sub> perovskite quantum dots with reduced defect density, enhanced crystallinity, higher phase purity, and near-unity photoluminescence quantum yield.
- The efficiency of CsPbI<sub>3</sub> perovskite quantum dot solar cells was enhanced from 14.07% to 15.72% together with enhanced storage stability.

**ABSTRACT** All-inorganic CsPbI<sub>3</sub> quantum dots (QDs) have demonstrated promising potential in photovoltaic (PV) applications. However, these colloidal perovskites are vulnerable to the deterioration of surface trap states, leading to a degradation in efficiency and stability. To address these issues, a facile yet effective strategy of introducing hydroiodic acid (HI) into the synthesis procedure is established to achieve high-quality QDs and devices. Through an in-depth experimental analysis, the introduction of HI was found to convert PbI<sub>2</sub> into highly coordinated [PbI<sub>m</sub>]<sup>2-m</sup>, enabling control of the nucleation numbers and growth kinetics. Combined optical and structural investigations illustrate that such a synthesis technique is beneficial for achieving enhanced crystallinity and a reduced density of crystallographic defects. Finally, the effect of HI is further reflected on the PV performance. The optimal device demonstrated a significantly improved power conversion efficiency of 15.72% along with enhanced storage stability. This technique illuminates a novel and simple methodology to regulate the formed species during

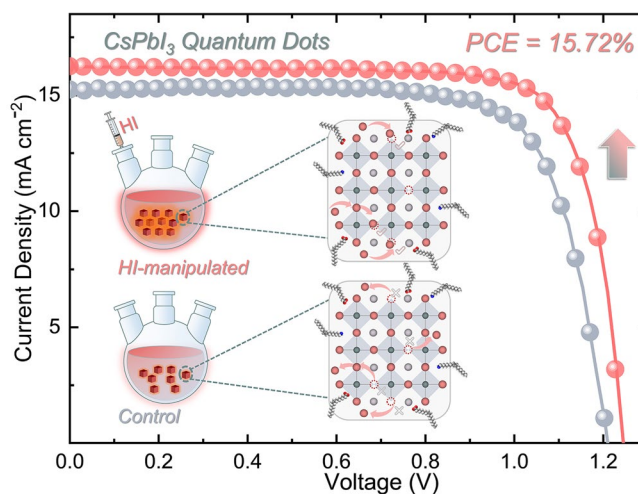

✉ Baomin Xu, xubm@sustech.edu.cn; Jianyu Yuan, jyyuan@suda.edu.cn; Wanli Ma, wlma@suda.edu.cn

<sup>1</sup> Department of Materials Science and Engineering, Southern University of Science and Technology, Shenzhen 518055, People's Republic of China<sup>2</sup> Institute of Functional Nano & Soft Materials (FUNSOM), Soochow University, 199 Ren-Ai Road, Suzhou Industrial Park, Suzhou 215123, People's Republic of China<sup>3</sup> Department of Electrical and Computer Engineering, University of British Columbia, 2329 West Mall, Vancouver, BC V6T 1Z4, Canada<sup>4</sup> Department of Chemistry, Sungkyunkwan University, Suwon 16419, Republic of Korea<sup>5</sup> Jiangsu Key Laboratory of Advanced Negative Carbon Technologies, Soochow University, 199 Ren-Ai Road, Suzhou Industrial Park, Suzhou 215123, People's Republic of China<sup>6</sup> Jiangsu Key Laboratory for Carbon-Based Functional Materials & Devices, Soochow University, 199 Ren-Ai Road, Suzhou Industrial Park, Suzhou 215123, People's Republic of China

Published online: 29 June 2023



SHANGHAI JIAO TONG UNIVERSITY PRESS

Springer

synthesis, shedding light on further understanding solar cell performance, and aiding the design of future novel synthesis protocols for high-performance optoelectronic devices.

**KEYWORDS** CsPbI<sub>3</sub> perovskite quantum dots; In situ passivation; Surface trap states; Perovskite solar cell

## 1 Introduction

Solution-processed all-inorganic lead halides colloidal perovskite quantum dots (QDs) have been extensively studied as photo-electron conversion and emitting materials for optoelectronic applications [1-5]. They exhibit superior optical properties, such as a spectrally tunable bandgap, narrow emission width, and high photoluminescence quantum yield (PLQY) [5, 6]. Blessed with excellent properties, perovskite QDs quickly opened a new horizon in the optoelectronic field [7-9]. Perovskite QDs with inorganic cations, such as CsPbI<sub>3</sub>, have recently gained increasing attention due to superior ability in controlling size, shape and composition, as well as possessing a desired solar-cell optical bandgap of 1.73 eV [1, 10, 11]. Additionally, it was demonstrated that CsPbI<sub>3</sub> QDs can maintain a stable cubic (black) phase at room temperature, whereas bulk CsPbI<sub>3</sub> materials tend to convert into their nonfunctional  $\delta$ -phase (yellow) below a temperature of 320 °C [6, 12, 13]. These non-functional crystals demonstrate poor optoelectronic properties [14]. The superior phase stability in CsPbI<sub>3</sub> QDs is mainly accredited to the contributions of its high surface-to-volume ratio and attached capping ligands which sterically insulate the QDs from environmental damage [15-18].

While surface ligands ensure phase stability, their inherent insulating nature inevitably hinders charge transport [19, 20]. Layer-by-layer device deposition allows for the chemical removal of surface ligands. While this in theory improves charge transport along the semiconductor, it inescapably generates dangling bonds which act as trap states, impeding carrier diffusion and transport [10]. Surface post-processing is considered one of the most effective methods to eliminate unnecessary recombination centers generated from these ionic vacancy defects [17, 21]. Quite recently, great research efforts are concentrated on functional grouped organic molecules such as triphenyl phosphite [22], di-n-propylamine [20], GA<sup>+</sup> salts [23], and phenylethyl ammonium to minimize surface point defects induced recombination centers and enhance the dot-to-dot electronic coupling [24]. Moreover, significant previous work on perovskite QDs and PbX (S,

Se) QDs has shown that metal cations and inorganic ions can modulate the surface dangling bonds of QDs to promote charge transport [19, 25]. Solid-state post-processing passivation strategies for achieving lower surface defect state densities are mainly focused on the surface of the CsPbI<sub>3</sub> QD layer [26, 27]. However, trap states underneath remain insufficiently passivated. Additionally, based on the established colloidal synthetic protocols, PbI<sub>2</sub> serves as the sole source of iodide ions, which leads to an excessively high demand for PbI<sub>2</sub> within the crystal [28]. Such high Pb-rich requirements render a significant portion of unreacted Pb and Pb-related byproducts [29, 30]. Therefore, developing a simple and effective in situ strategy for minimizing the trap state density in QDs while reducing lead waste is of great significance.

In this work, we employ an in situ passivation method by introducing hydroiodic acid (HI) into the precursor solution to obtain high-quality CsPbI<sub>3</sub> QDs. We systematically tuned the added concentration of HI and characterized the structural, optical, electrical, and morphological properties. The deployment of the in situ passivation strategy was found to not only enhance the crystallinity but also lead to a reduced defect density. These improvements stem from the HI-driven conversion of the uncoordinated Pb<sup>2+</sup> ion into [PbI<sub>m</sub>]<sup>2-m</sup>. A suitable iodine ion introduction can guarantee the fabrication of a CsPbI<sub>3</sub> QD matrix with decreased non-radiative recombination caused by iodine-vacancy point defects, forming compact low defect-density polycrystalline QD films [31-33]. Consequently, this passivation technique yielded a best power conversion efficiency (PCE) of 15.72% together with enhanced storage stability.

## 2 Experimental

### 2.1 Materials

1-octadecene (ODE, tech. grade, 90%, J&K), Cs<sub>2</sub>CO<sub>3</sub> (99.9%, J&K), oleic acid (OA, tech. grade, 90%, Alfa), oleylamine (OLA, tech. grade, 90%, Alfa), lead iodine (PbI<sub>2</sub>, 99.0%, Advanced Election Tech.), titanium tetrachloride (TiCl<sub>4</sub>, ≥ 98%, Sinopharm Chemical Reagent Co., Ltd.), n-hexane (> 98%, Alfa Aesar), methyl acetate (MeOAc, anhydrous

99.5%, Sigma), hydroiodic acid (HI, 95%, Sigma), 1-Octane (anhydrous, 99.8%, Sigma), Poly[bis(4-phenyl)(2,4,6-trimethylphenyl)amine]: PTAA ( $M_n = 17,000 \text{ g mol}^{-1}$ , Xi'an Polymer Light Technology Corp) were purchased and used as received without further purification.

## 2.2 Synthesis and Purification of CsPbI<sub>3</sub> QDs

PbI<sub>2</sub> (1 g) and ODE (50 mL) were added into a 250 mL round bottom three-neck flask. The solution is then slowly heated to 90 °C under vacuum for at least one hour. Then, the flask is filled with nitrogen (N<sub>2(g)</sub>) and injected with 5 mL of both OA and OLA. The flask is then put again under vacuum and subsequently filled with N<sub>2</sub>. Next, the solution is slowly heated to 165 °C. As this temperature stabilizes, the pre-heated transparent Cs-oleate (8 mL) is swiftly injected into the Pb-I-precursor and allowed to react for a reaction time of 5 s. The solution is then quickly cooled by using an ice-water bath. In the HI-manipulated CsPbI<sub>3</sub> QDs synthesis, different feeding volumes of HI solution (50, 100, and 150 μL) were loaded into the PbI<sub>2</sub>-precursor, with an identical remaining procedure. For purification, the crude solution of CsPbI<sub>3</sub> QDs was precipitated by adding MeOAc (the volume ratio of methyl acetate (MeOAc) and the as-synthesized solution is 3:1), and the mixture was centrifuged at 8000 rpm for 5 min. The supernatant was discarded, and precipitates were redispersed in 18 mL of hexane. Then, the solution was mixed with 18 mL MeOAc and centrifuged at 8000 rpm for 3 min. The supernatant was discarded, and the received precipitate was redispersed in 20 mL hexane. Finally, the solution was centrifuged at 4000 rpm for 5 min to remove large aggregates, while the supernatant was collected. The obtained supernatant was stored at -5 °C for 24 h in a dark condition and centrifuged again at 4000 rpm for 5 min to precipitate byproducts and unreacted materials. The final precipitate was dried through a rotary evaporator and redispersed into octane with a concentration of 70 mg mL<sup>-1</sup>.

## 2.3 CsPbI<sub>3</sub> QD Solar Cell Fabrication and Characterizations

CsPbI<sub>3</sub> QD solar cells were constructed with a structure of glass/fluorine-doped tin dioxide: (FTO)/TiO<sub>2</sub>/CsPbI<sub>3</sub>QDs/Poly[bis(4-phenyl)(2,4,6-trimethylphenyl)amine]:(PTAA)/

MoO<sub>3</sub>/Ag. FTO substrates were ultrasonically cleaned in deionized water, acetone, and isopropanol several times. Next, compact TiO<sub>2</sub> films were deposited onto the cleaned FTO substrates via chemical bath deposition at 70 °C [34]. The films were annealed at 200 °C for 30 min and then, further treated with UV-ozone for 20 min. The CsPbI<sub>3</sub> QD solution (70 mg mL<sup>-1</sup> in octane) was spin-casted on the substrate at 1000 rpm for 20 s and 2000 rpm for 15 s. Then, 120 μL of methyl acetate (MeOAc) was dropped on the as-casted CsPbI<sub>3</sub> QDs layer for 5 s to ignite the solid ligand exchange process to remove the long chain ligands, followed with a final centrifugation at 2000 rpm for 20 s. This fabrication process was repeated four times to establish a thick QD film of ~400 nm to provide sufficient light absorption. Then, the film was immersed into the solution of Guanidine thiocyanate (GASCN) in ethyl acetate (EtOAc) followed by a rinse and drying in MeOAc and N<sub>2</sub>, respectively. The CsPbI<sub>3</sub> QD film fabrication process was conducted in a dry air-filled glove box at room temperature with relative humidity below 10%. The doped PTAA toluene solution (15 mg mL<sup>-1</sup>) was spin-coated on top of the CsPbI<sub>3</sub> QD films at 3000 rpm for 40 s. Finally, 8- and 120-nm-thick layers of MoO<sub>3</sub> and Ag were deposited by thermal evaporation under a vacuum of  $1 \times 10^{-6}$  mbar, respectively. The active area of the cell was defined as 0.0725 cm<sup>2</sup> through a shadow mask. The *J-V* characteristics of the devices were acquired using a Keithley 2400 digital source meter under simulated air-mass 1.5G (AM 1.5 G) spectrum at 100 mW cm<sup>-2</sup> with a solar simulator (Class AAA, 94023 A-U, Newport). The light intensity was calibrated to 100 mW cm<sup>-2</sup> by a National Renewable Energy Laboratory certified monocrystalline silicon reference solar cell (91 150 V, Newport Oriol).

## 3 Results and Discussion


### 3.1 Investigation of Optical and Carrier Dynamics Properties

The colloidal CsPbI<sub>3</sub> QDs were synthesized via the reported hot-injection protocol using oleic acid (OA) and oleylammonium (OLA) ligands [35]. The HI-manipulated CsPbI<sub>3</sub> QDs utilized in this research were synthesized by first injecting vary volumes of HI into PbI<sub>2</sub>-precursor, followed by the injection of Cs-oleate, as illustrated in Fig. 1a, b. We investigated the UV-vis absorbance and steady-state

photoluminescence (PL) spectra of the CsPbI<sub>3</sub> QD solution with/without (w/wo) HI-manipulation. For HI-modified QDs, the PL emission peaks display a gradual red shift from 685 to 691 nm for control and QDs with HI manipulation below 100  $\mu$ L, except for the 150  $\mu$ L HI sample, which exhibits opposite trends (Fig. S1). The optical bandgaps were extracted from the Tauc plots in Fig. S2 with a value of 1.785 ( $\pm$ 0.005) and 1.776 ( $\pm$ 0.003) eV for the control and optimal HI devices, respectively. It is noted that HI manipulation exhibits a negligible impact on the optical absorption (Fig. S3), while creating an emission shoulder near the main PL peak position at 688 nm for the 150  $\mu$ L sample (Fig. S1). This emission shoulder is attributed to the emergence of nanowires throughout the crystal morphology. To examine the passivation effect of HI on CsPbI<sub>3</sub> QDs, we performed time-resolved photoluminescence (TRPL), PL quantum yield (PLQY), 2D-PL, and transient absorption spectra (TAS) measurements. Figure 1c, d depicts the 2D TAS patterns for CsPbI<sub>3</sub> QDs w/wo HI. The positions of the photo-bleaching peak at 5 ps in the initial signal emergence are well-aligned with the exciton peaks from steady-state absorption. The photo-excited carriers then rapidly funnel to the low-energy sites [36]. While the HI-manipulated sample exhibits minor energy offset, the control sample exhibits a gradually redshift of the photo-bleaching peak characteristic (Fig. S5a–b). The reduced surface iodine-vacancy-induced lattice disorder is attributed to the lowered energy offset, which indicates less disorder and energy funneling toward undesired band-tail states [37]. The derived decay curves of ground states bleaching and photon-induced absorption from TAS spectra are displayed in Fig. S5c–d, and Table S1 provides a detailed list of the fitted parameters. As shown in Figs. S4 and 1e, the observed TRPL results exhibit a bi-exponential decay characteristic, and the fitted average PL lifetimes ( $\tau_{\text{avg}}$ ) are 35.74 and 58.51 ns for the samples w/wo HI passivation (Table S2), respectively. This prolonged exciton recombination dynamic implies the successful suppression of surface trap-induced nonradiative recombination [36, 38, 39]. In addition, the optimal HI dosed QDs observed a near-unity PLQY of 94%, whereas the control is merely 78% (Fig. 1d, Table S3), indicating excellent surface passivation [40]. These results further demonstrate that the addition of HI aids in obtaining CsPbI<sub>3</sub> QDs with lower crystallographic defects. These observations are in good agreement with the results of TA characterizations.

### 3.2 Crystallization and Morphology Examination of CsPbI<sub>3</sub> QDs


To reveal the effects on the crystal morphology, a set of transmission electron microscope (TEM) images were acquired. As shown in Fig. 2a, the deployment of the HI assisted in situ synthetic procedure did not change the morphology below 100  $\mu$ L. Surpassing this volume threshold leads to the emergence of nanowires (Figs. 2a and S1, S6). Good size uniformity is crucial for charge carrier non-radiative recombination as a wide size distribution causes the broadening of the band-tail states which aggravates the energetic disorder [41, 42]. To analyze this, TEM images were obtained and the QD size distribution was examined. As shown in Fig. 2a (the insets), the histograms are fitted using a Gaussian curve to determine the average size. The mean particle size of the control and optimal HI-manipulated CsPbI<sub>3</sub> QDs are 10.25 and 11.84 nm, respectively. The results indicate that a significant improvement in the size uniformity, along with relatively larger QDs size. In addition, structural characterizations were also conducted. Spherical aberration corrected TEM was used to observe the atomic structures and characterize the crystallinity of the CsPbI<sub>3</sub> QDs, as shown in Fig. 2b. Both the control and HI-influenced CsPbI<sub>3</sub> QDs have a lattice separation of 0.628 nm, corresponding to the (100) crystal facet of the cubic structure [1, 43, 44]. Using these TEM images, the crystalline structures were analyzed by measuring the fast Fourier transformation (FFT) (Fig. 2b) and compared with the X-ray diffraction (XRD) patterns (Fig. 2c). These results indicate an ideal cubic phase along with an unmodified zone axis after the introduction of HI [45]. Moreover, as shown in Fig. 2c, the XRD patterns suggest that the crystal structures are unaltered after HI addition. There is a notable peak of PbI<sub>2</sub> at roughly 11.8° in the control sample, pointing to the presence of residual unreacted Pb-related byproducts [28, 46, 47]; however, the PbI<sub>2</sub> diffraction peak disappears for samples with a feeding volume exceeding 50  $\mu$ L. The diffraction peaks can be well indexed to the pure cubic CsPbI<sub>3</sub> perovskite crystal structure, which is in good agreement with the standard data. Notably, the XRD diffraction intensity becomes stronger as the HI volume was kept below 100  $\mu$ L. Surpassing this threshold leads to a substantial intensity decrease, while the cubic crystal structure is still retained. The XRD patterns of CsPbI<sub>3</sub> QDs are consistent with the spherical aberration

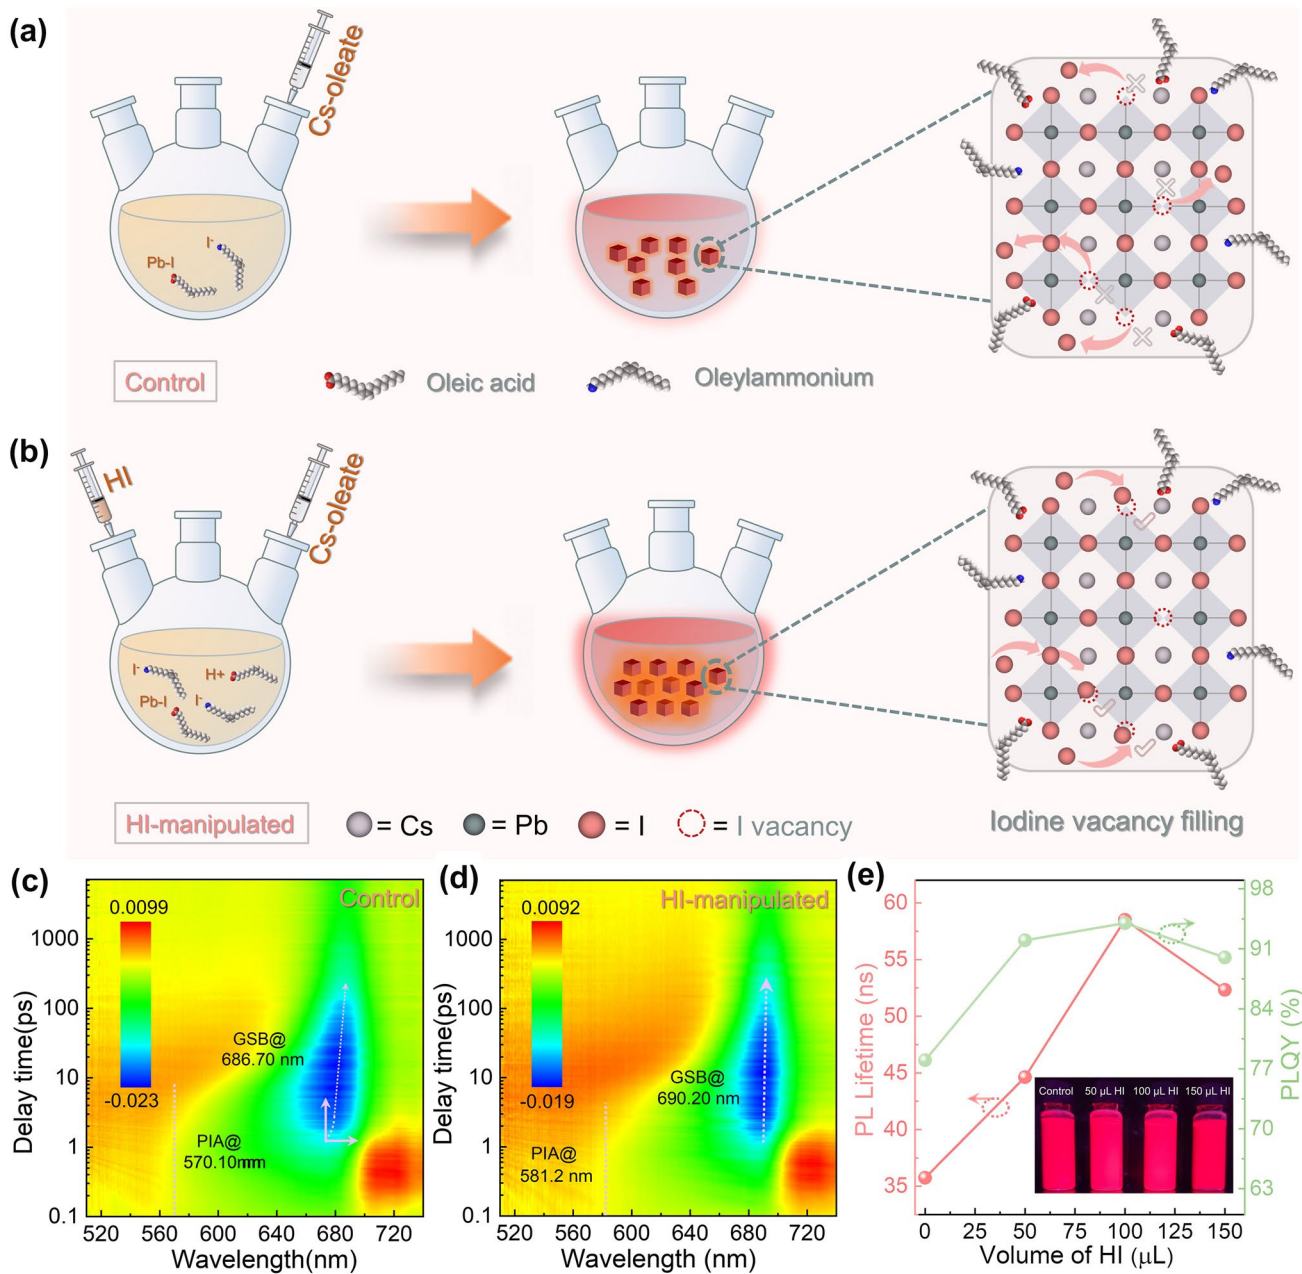

**Fig. 1** **a, b** Schematic illustration of CsPbI<sub>3</sub> QDs synthesis process w/o HI manipulation. **c, d** Transient absorption maps of control and HI-manipulated CsPbI<sub>3</sub> QDs. and **e** PLQY and the fitted TRPL lifetimes of CsPbI<sub>3</sub> QDs synthesized with different HI volumes (Inset: photographs of QD solutions under UV light illumination)

corrected TEM measurements, illuminating the improved QD crystallinity. To verify the morphological variation, we further investigate the results after overloading the HI additive. Like above, the optical and structural properties of the CsPbI<sub>3</sub> QDs with overloaded HI manipulation were studied by measuring the UV–vis absorption spectra and

TEM imaging. Interestingly, the absorption remains relatively unchanged (Fig. S7). However, via TEM imaging, we notice the formation of large aggregate crystals with irregular shapes and significantly increased nucleation sites (Fig. S8). Fundamental understanding into the chemical nature of nucleate numbers and growth process of CsPbI<sub>3</sub> QDs can be

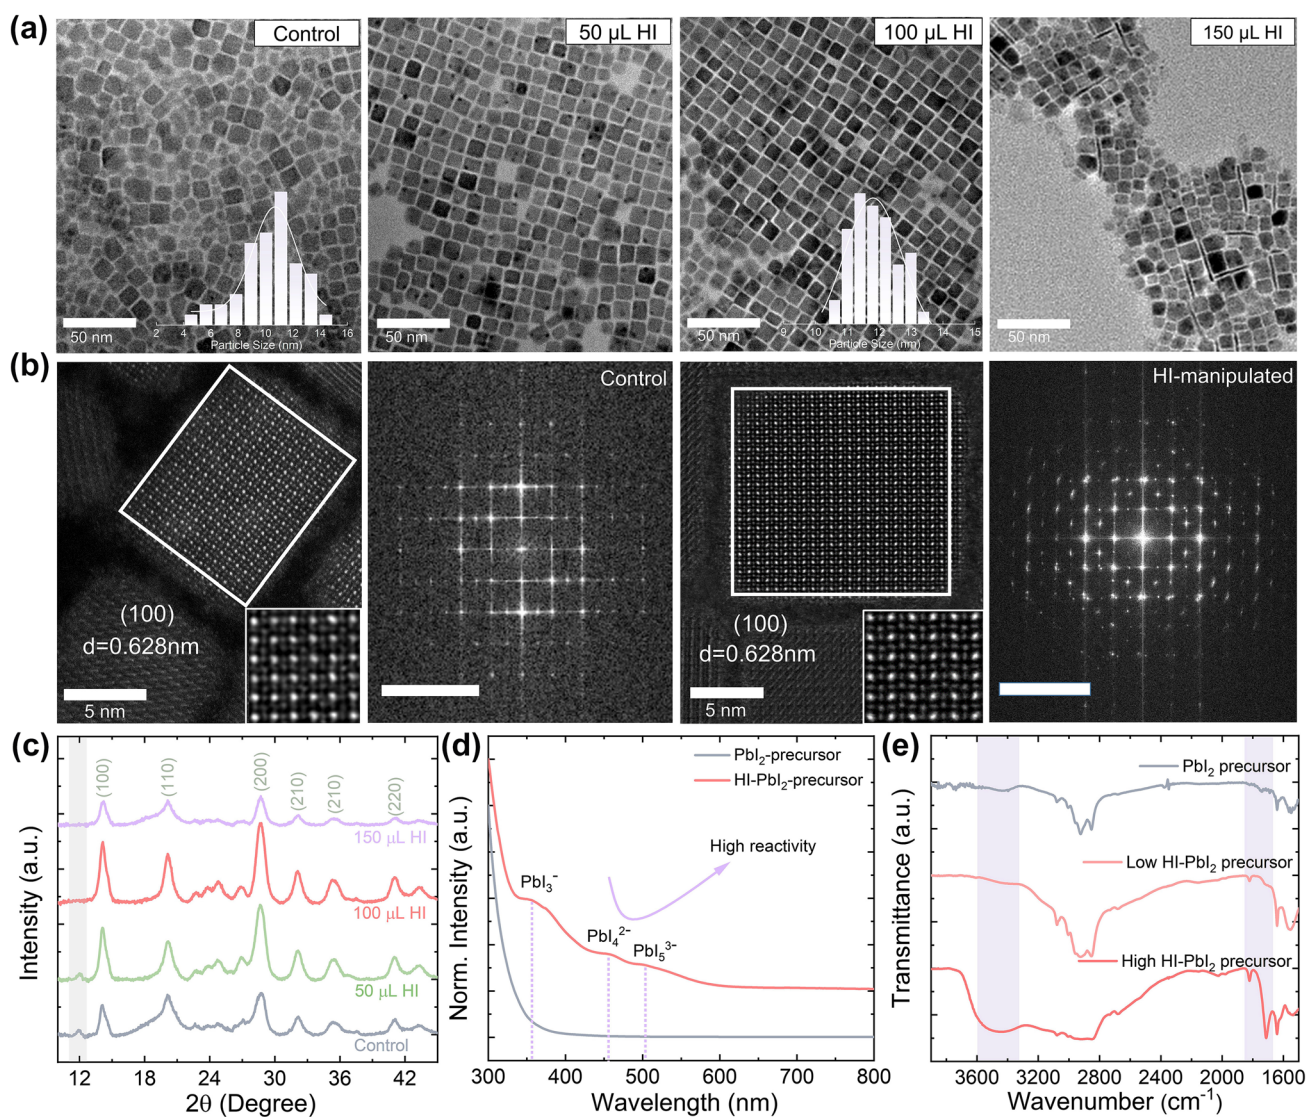

**Fig. 2** **a** TEM images of the CsPbI<sub>3</sub> QDs synthesized with varying HI concentrations (Inset: the statistic distribution of grain sizes extracted from the corresponded TEM images). **b** The spherical aberration corrected TEM images of the control and optimized HI-manipulated CsPbI<sub>3</sub> QDs, along with the corresponding FFT patterns (Inset: high-magnification TEM images shown the lattice distance of 0.628 nm of (100) crystallographic plane). **c** Evolution of XRD patterns of the CsPbI<sub>3</sub> QDs synthesized with different HI volumes. **d** UV-vis absorption spectra and FTIR spectra of PbI<sub>2</sub>-OA-OLA precursor w/o the addition of HI

discovered through these HI additives to promote the generation of polyiodide colloids. The iodine anions functioning as a Lewis base can interact strongly with halogenated metal molecules through noncovalent interactions, resulting in halogen bonding [48]. Also, UV-vis, XRD, and FTIR characterizations of the PbI<sub>2</sub> and HI-PbI<sub>2</sub>-precursors were carried out to determine how the introduced acid impacts the crystallographic growth kinetics. Several iodide-coordinated plumbate ions are observed in the HI-PbI<sub>2</sub>-precursor,

as shown in Fig. 2d, and their absorption peaks are consistent with the previous observations [49, 50]. We found that the high I<sup>-</sup> concentration can trigger the generation of lead acid species including PbI<sub>3</sub><sup>-</sup> to PbI<sub>4</sub><sup>2-</sup> and PbI<sub>5</sub><sup>3-</sup>, which indicates that I<sup>-</sup> cooperates with the lead Lewis acid species to form highly coordinated polyiodide colloids. The XRD pattern seen in Fig. S9a further supports similar findings. The potential dynamics process of existing specials in Pb-I-precursor w/o HI manipulation seen in Fig. S10.

As shown in Fig. 2e, in the  $\text{PbI}_2$ -precursor without HI, the stretching vibration of  $\text{R-NH}_3^+$  is at  $3433\text{ cm}^{-1}$  due to the protonation interaction with OA [20]. After the addition of HI, the stretching vibration is intensified and red-shifted to  $3443\text{ cm}^{-1}$  due to the promoted protonation process and increased coordination of  $\text{I}^-$  with the  $\text{PbI}_m^{[2-m]}$  colloids. The FTIR results further demonstrate that  $\text{I}^-$  works well with the lead acid species to form high-coordination centers. Since the reactivity of  $[\text{PbI}_m]^{2-m}$  increases with the coordinate number  $m$ ,  $\text{PbI}_4^{2-}$  and  $\text{PbI}_5^{3-}$  display have higher reactivity than  $\text{PbI}_3^-$  [50]. Moreover, the additionally introduced HI raised the critical concentration of monomer, as shown in Fig. S9b. It is therefore plausible to conclude that the highly coordinated  $[\text{PbI}_m]^{2-m}$  induced by HI introduction can surpass the limit of the reaction barrier to form  $\text{CsPbI}_3$  QDs, and thereby well manipulates the nucleate number and growth kinetics of  $\text{CsPbI}_3$  QDs, leading to enhanced crystallinity and phase purity.


### 3.3 Analysis of $\text{CsPbI}_3$ QD Film Variations

To gain insight into variations of the  $\text{CsPbI}_3$  QD films w/o HI, grazing incidence wide-angle X-ray scattering (GIWAXS), top-view atomic force microscopy (AFM) and 2D-photoluminescence (2D-PL) mapping were further employed. The crystallinity and orientation preference of  $\text{CsPbI}_3$  QDs films were evaluated by synchrotron-based 2D-GIWAXS, as shown in Fig. 3a, b. Both samples display strong characteristic X-ray diffractions for  $\text{CsPbI}_3$  QDs. The 2D-GIWAXS diffraction pattern of the control sample exhibits diffraction intensity scattered around rings, indicating randomly orientation. In contrast, the HI manipulated film shows more localized diffractions peaks, suggesting preferable orientation. To examine the preferred direction of the crystallization process, we analyzed the extracted in-plane ( $q_{xy}$ ) diffractions peak curves. The diffraction patterns at 1.015, 1.429, 1.895, 2.029, and 2.258  $\text{\AA}$  correspond to the (100), (110), (111), (200), and (210) crystal planes for the typical  $\text{CsPbI}_3$  QDs structure, respectively [51]. We observed that the intensity of (100) lattice plane peak exhibits an evidently stronger in HI-manipulated QD sample, whereas the (200) remains consistent with the control (Fig. S11). As shown in Fig. 3c, d, both films exhibit a closely packed QD matrix with similar surface topography and roughness, confirming that the optimal volume of HI

has a negligible impact on the  $\text{CsPbI}_3$  QD film. In addition, we performed 2D-PL mapping measurements of  $\text{CsPbI}_3$  QD films (Fig. 3e, f). The HI-manipulated films display an enhanced and more uniform PL emission intensity relative to the control. These results indicate that the introduced HI provides huge potential in controlling the crystal growth to acquire superior crystallinity of  $\text{CsPbI}_3$  QDs. To gain insight into the films surface chemistry variations, we performed X-ray photoelectron spectroscopy (XPS). The XPS core-level spectra of the constituent elements are shown in Fig. S12a–d. The bonding states corresponding to the Cs 3d, Pb 4f, and I 3d core levels of the HI-manipulated  $\text{CsPbI}_3$  QDs shift marginally to higher binding energy regions with respect to the control, which can be attributed to the enhanced chemical interaction between surface lead and iodine ions. For  $\text{CsPbI}_3$  QDs synthesized with the HI, the ratio of I<sub>3</sub>/Pb is increased, and values of 1.56 and 1.79 are calculated for the control and HI-manipulated  $\text{CsPbI}_3$  QDs, respectively (Fig. S13). These results show that the  $\text{CsPbI}_3$  QDs was successfully restored by filling in the iodide vacancies, resulting in improved optoelectronic properties of the  $\text{CsPbI}_3$  QDs [18, 31].

### 3.4 Photovoltaic Performance of $\text{CsPbI}_3$ QD Solar Cells

Having examined the effective defects passivation of HI-manipulation on  $\text{CsPbI}_3$  QDs, it is important to explore whether the regulations can be combined and reflected on the performance of PV device. As mentioned above, the solar cells were fabrication with the following configuration: glass/FTO/ $\text{TiO}_2$ / $\text{CsPbI}_3$  QDs/PTAA/ $\text{MoO}_3$ /Ag. A cross-sectional SEM view of the device is shown in Fig. 4a.  $\text{CsPbI}_3$  QD solar cells were fabricated by employing  $\text{CsPbI}_3$  QDs w/o HI additive. Devices using HI volumes of 50, 100 and 150  $\mu\text{L}$  were investigated with an optimal device performance achieved at 100  $\mu\text{L}$  (Fig. S14). Consequently, this volume, denoted as HI-manipulated, is the additive feeding volume used in all studies hereafter described. The  $J$ - $V$  characteristics (under AM 1.5 G illumination with light intensity of  $100\text{ mW cm}^{-2}$ ) of the control and HI-manipulated  $\text{CsPbI}_3$  QD solar cells are shown in Fig. 4b. We obtained the HI-manipulated device with a champion efficiency of 15.72%, an open-circuit voltage ( $V_{\text{OC}}$ ) as high as 1.25 V, a short-circuit current density ( $J_{\text{SC}}$ ) of  $16.25\text{ mA cm}^{-2}$ , and a fill factor (FF) of 77.39%. For the control, an output of 14.07%

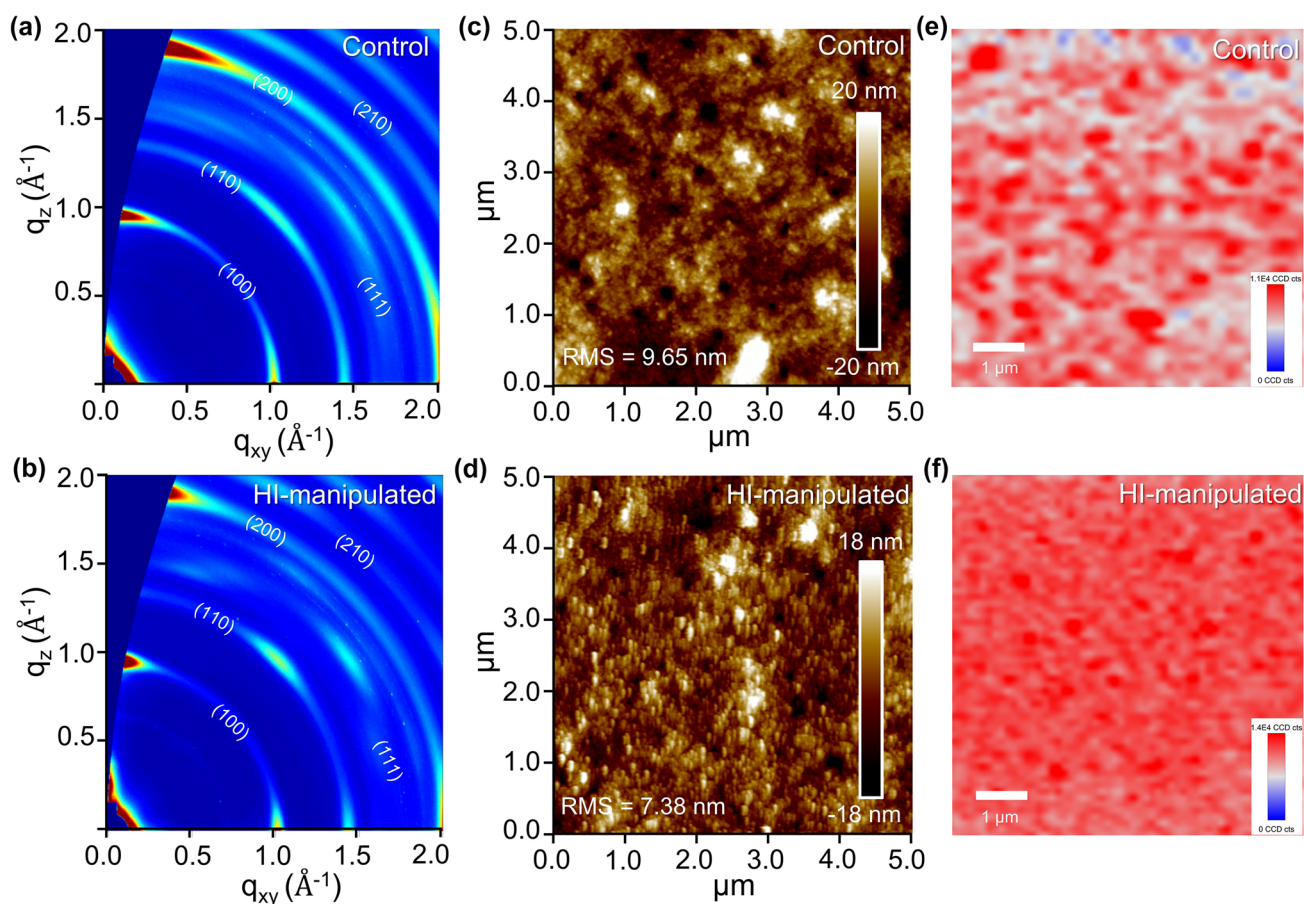


**Fig. 3** The control and optimal HI manipulated CsPbI<sub>3</sub> QD films measurements of **a, b** 2D grazing incidence wide-angle X-ray scattering (GIWAXS) patterns, **c, d** Top-view atomic force microscopy (AFM) images and **e, f** 2D photoluminescence mapping

is achieved. The  $J$ - $V$  curves under the forward scan direction are shown in Fig. S15. Detailed PV parameters extracted from the  $J$ - $V$  curves in both forward and reverse scan directions are shown in Table S4. It should be noted that the HI-manipulated CsPbI<sub>3</sub> QD solar cell demonstrates negligible hysteresis compared with the control device, which attributed to the effective surface iodine vacancies filling, leading to reduced ion migration. The improved passivation effect is unimpaired to reflect on the final PV outcome. The external quantum efficiency (EQE) as a function of wavelength for the solar cells is shown in Fig. 4c. As expected, the spectral response of the HI-manipulated device in the 380–700 nm wavelength range is superior to that of the control, which contributes to the improved  $J_{SC}$ . The integrated current density from the EQE is 15.42 mA cm<sup>-2</sup>, which is in good agreement with the observed  $J_{SC}$  from the  $J$ - $V$  characteristics. To explore whether the enhanced crystallinity

will affect stability, the storage stability of the HI-manipulated CsPbI<sub>3</sub> QDs was recorded. After storage under dry air conditions at room temperature for 200 h, the HI-manipulated CsPbI<sub>3</sub> QD device retained 80.68% of its original PCE, while the control device showed a 37.43% PCE loss (Fig. 4d). The lattice deformation of the Pb-centered octahedral framework, which may be triggered by ion migration, causes the symmetry lowering. The in situ HI-manipulated CsPbI<sub>3</sub> quantum dots were effectively restored by filling in the iodide vacancies, which led to the decreased ion migration, aiding to the reduced hysteresis and improved storage stability. In light of this, we attribute the notably improved storage stability to the effective passivated surface traps. To investigate the device charge recombination dynamic behaviors, electrochemical impedance spectroscopy (EIS) measurements were employed. The extracted parameters of the equivalent circuit are listed in Table S5. As shown in



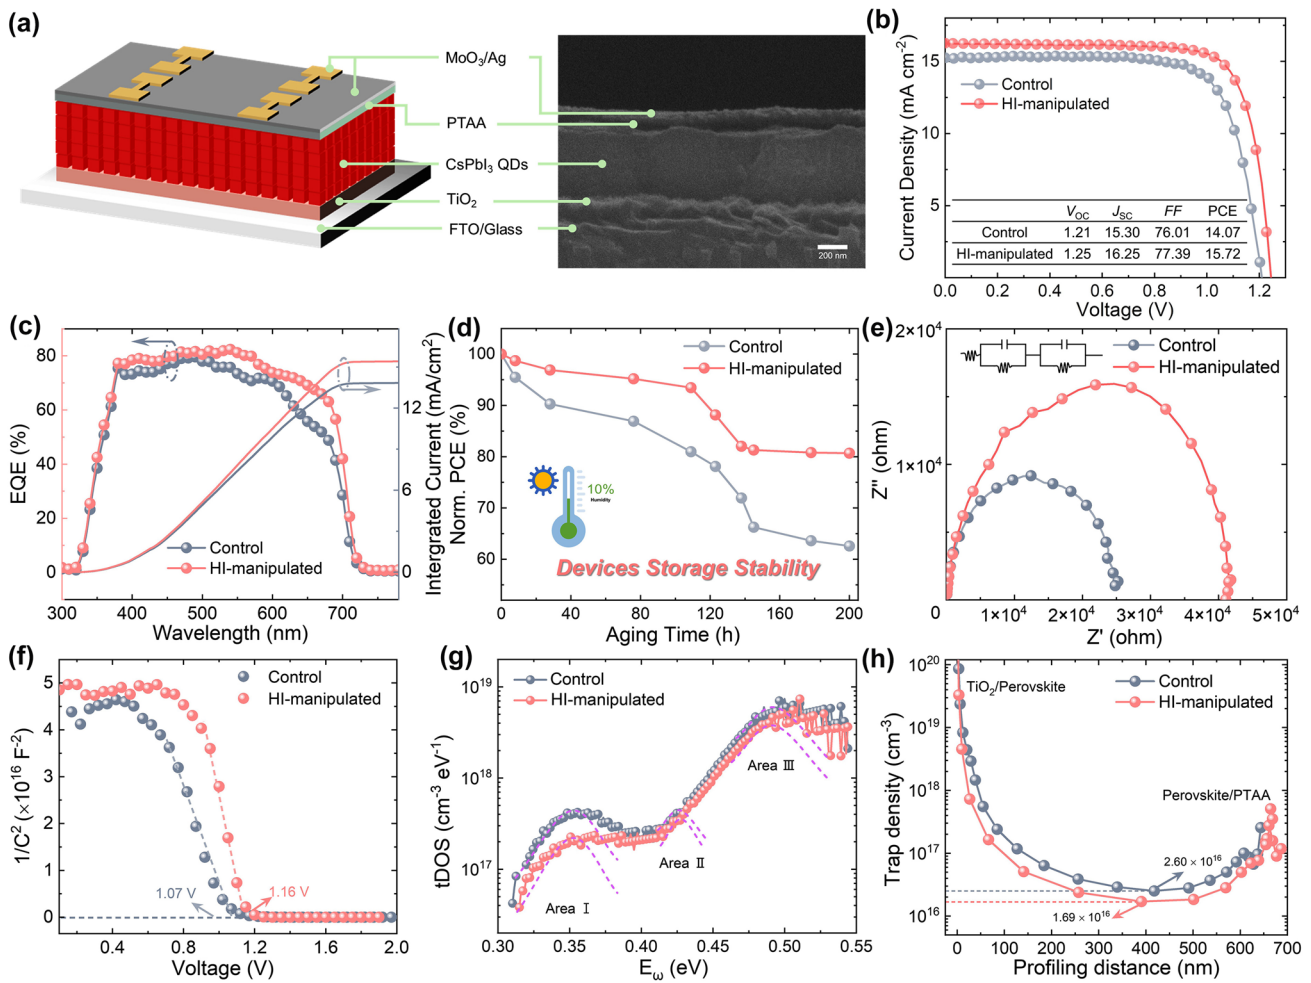

**Fig. 4** **a** Schematic illustration of device structure and the corresponding cross-sectional SEM image of CsPbI<sub>3</sub> QD solar cell. **b** *J*–*V* curves of the devices based on control and 100 μL HI-manipulated CsPbI<sub>3</sub> QDs. Inset: The detailed devices parameters of champion solar cells. **c** EQE spectra and integrated current density of optimized CsPbI<sub>3</sub> QD solar cells. **d** Evolution of the PCE of the optimized CsPbI<sub>3</sub> QD solar cells in dry air conditions. **e** Nyquist plots, **f** Mott–Schottky plots, **g** Trap density of states (tDOS) and **h** dependence of the trap densities on the profiling distances of optimized devices based on control and 100 μL HI-manipulated CsPbI<sub>3</sub> QDs

Fig. 4e, the series resistance ( $R_s$ ) and increased recombination resistance ( $R_{rec}$ ) of the HI-manipulated CsPbI<sub>3</sub> QD devices indicate that the recombination process is effectively suppressed, resulting in improved charge transfer [52]. We further characterized the built-in potentials ( $V_{bi}$ ) of the two devices by using Mott–Schottky (M–S) analysis, as shown in Fig. 4f. The relationship between the junction capacitance and DC voltage bias can be described by the following equation [53]:

$$\frac{A^2}{C^2} = \frac{2(V_{bi} - V)}{qN\epsilon\epsilon_0}$$

where  $A$  is the active area of the device,  $V$  refers to the applied DC voltage,  $q$  is the elementary charge,  $N$  refers to the impurity doping density, and lastly,  $\epsilon$  and  $\epsilon_0$  refer to vacuum and relative permittivity, respectively. The  $V_{bi}$  can be calculated using the x-intercept of linear regime of M–S plot. The fitting result shows a larger  $V_{bi}$  for the HI-manipulated CsPbI<sub>3</sub> QDs compared with the control device (1.16 V), which follows a similar trend to the  $V_{OC}$  measured from the *J*–*V* curves. The enhanced  $V_{bi}$  could be attributed the reduction in non-radiative recombination through this passivation technique [54]. Moreover, thermal admittance spectroscopy analysis was carried out to obtain insight into the energetic distribution of trap density of states (tDOS). As shown in Fig. 4g, the tDOS with an energy level above

0.40 eV (area II and area III) decreased slightly with an obvious drop in the energy region between 0.30 and 0.40 eV (area I), indicating the effective passivation of shallower traps states, i.e., iodine-vacancy dominated shallow level defects [55, 56]. In addition, as shown in Fig. 4h, the best performing control and HI-manipulated devices exhibit a minimal trap states of  $2.60 \times 10^{16}$  and  $1.69 \times 10^{16} \text{ cm}^{-3}$ , respectively. These results evidently confirm that the HI-manipulated CsPbI<sub>3</sub> QD device exhibits improved charge transport and reduced recombination, contributing to the prominent enhancement of  $J_{sc}$ , and thus delivering overall enhanced performance of the CsPbI<sub>3</sub> QD PV device.

## 4 Conclusion

In summary, we developed a facile yet effective in situ passivation strategy of CsPbI<sub>3</sub> to acquire high-quality CsPbI<sub>3</sub> QDs. We revealed that a high I<sup>-</sup> concentration is able to trigger highly coordinated polyiodide colloids from PbI<sub>3</sub><sup>-</sup> to PbI<sub>4</sub><sup>2-</sup> and PbI<sub>5</sub><sup>3-</sup>, leading to higher crystallization and phase purity. We also demonstrated that the HI-manipulated CsPbI<sub>3</sub> QDs possess a reduction in non-radiative recombination and near-unity PLQY by filling in surface iodine vacancies. Benefitting from the effective surface defects manipulation through the optimized feeding volume of HI, we obtained the champion PCE of 15.72% together with an enhanced storage stability. Our study provides fundamental insights into the nano-synthesis reaction process and blazes a new trail of controlling the nucleation and growth kinetics of CsPbI<sub>3</sub> QDs. We highly expect that the present synthetic method can be extended to the regulations of other nanomaterials for high-performance optoelectronic applications.

**Acknowledgements** This work was financially supported by the National Key Research and Development Program of China (No. 2021YFB3800101 and 2022YFE0110300), National Natural Science Foundation of China (No. U19A2089, 52261145696, 52073198, 92163114, and 22161142003), Natural Science Foundation of Jiangsu Province (BK20211598), “111” project, the Young Elite Scientist Sponsorship Program by CAST, Collaborative Innovation Center of Suzhou Nano Science and Technology, Soochow University.

**Author Contributions** J. S. and B. C-K. conceived the project and did this study under the supervision of B. X., W. M. and J. Y.; J. S., X. Z., C. Z., Y. Z., X. L. and J. G. contributed to the data collection, analysis and discussion; D-H. K. contributed to GIWAX measurements. The manuscript was drafted and revised by J. S., B. C-K., J. Y., W. M., and B. X. with contributions from all authors.

**Funding** Open access funding provided by Shanghai Jiao Tong University.

## Declarations

**Conflict of interest** The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

**Open Access** This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons licence, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons licence, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons licence and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this licence, visit <http://creativecommons.org/licenses/by/4.0/>.

**Supplementary Information** The online version contains supplementary material available at <https://doi.org/10.1007/s40820-023-01134-1>.

## References

1. A. Swarnkar, A.R. Marshall, E.M. Sanehira, B.D. Chernomordik, D.T. Moore et al., Quantum dot-induced phase stabilization of alpha-CsPbI<sub>3</sub> perovskite for high-efficiency photovoltaics. *Science* **354**(6308), 92–95 (2016). <https://doi.org/10.1126/science.aag2700>
2. K. Lin, J. Xing, L.N. Quan, F.P.G. de Arquer, X. Gong et al., Perovskite light-emitting diodes with external quantum efficiency exceeding 20 percent. *Nature* **562**(7726), 245–248 (2018). <https://doi.org/10.1038/s41586-018-0575-3>
3. N. Wang, L. Cheng, R. Ge, S. Zhang, Y. Miao et al., Perovskite light-emitting diodes based on solution-processed self-organized multiple quantum wells. *Nat. Photonics* **10**(11), 699–704 (2016). <https://doi.org/10.1038/nphoton.2016.185>
4. M. Yuan, L.N. Quan, R. Comin, G. Walters, R. Sabatini et al., Perovskite energy funnels for efficient light-emitting diodes. *Nat. Nanotechnol.* **11**(10), 872–877 (2016). <https://doi.org/10.1038/nnano.2016.110>
5. C.Y. Huang, H. Li, Y. Wu, C.H. Lin, X. Guan et al., Inorganic halide perovskite quantum dots: a versatile nanomaterial platform for electronic applications. *Nano-Micro Lett.* **15**(1), 16 (2022). <https://doi.org/10.1007/s40820-022-00983-6>
6. S. Lim, S. Han, D. Kim, J. Min, J. Choi et al., Key factors affecting the stability of CsPbI<sub>3</sub> perovskite quantum dot solar cells: a comprehensive review. *Adv. Mater.* **35**(4), 2203430 (2022). <https://doi.org/10.1002/adma.202203430>

7. X. Mei, D. Jia, J. Chen, S. Zheng, X. Zhang, Approaching high-performance light-emitting devices upon perovskite quantum dots: Advances and prospects. *Nano Today* **43**, 101449 (2022). <https://doi.org/10.1016/j.nantod.2022.101449>
8. S.-T. Ha, R. Su, J. Xing, Q. Zhang, Q. Xiong, Metal halide perovskite nanomaterials: synthesis and applications. *Chem. Sci.* **8**(4), 2522–2536 (2017). <https://doi.org/10.1039/c6sc04474c>
9. S. Lim, D.H. Lee, H. Choi, Y. Choi, D.G. Lee et al., High-performance perovskite quantum dot solar cells enabled by incorporation with dimensionally engineered organic semiconductor. *Nano-Micro Lett.* **14**(1), 204 (2022). <https://doi.org/10.1007/s40820-022-00946-x>
10. E.M. Sanehira, A.R. Marshall, J.A. Christians, S.P. Harvey, P.N. Ciesielski et al., Enhanced mobility CsPbI<sub>3</sub> quantum dot arrays for record-efficiency, high-voltage photovoltaic cells. *Sci. Adv.* **3**(10), eaao4204 (2017). <https://doi.org/10.1126/sciadv.aao4204>
11. J. Xue, J.-W. Lee, Z. Dai, R. Wang, S. Nuryyeva et al., Surface ligand management for stable FAPbI<sub>3</sub> perovskite quantum dot solar cells. *Joule* **2**(9), 1866–1878 (2018). <https://doi.org/10.1016/j.joule.2018.07.018>
12. Q.A. Akkerman, G. Raino, M.V. Kovalenko, L. Manna, Genesis, challenges and opportunities for colloidal lead halide perovskite nanocrystals. *Nat. Mater.* **17**(5), 394–405 (2018). <https://doi.org/10.1038/s41563-018-0018-4>
13. X. Ling, J. Yuan, W. Ma, The rise of colloidal lead halide perovskite quantum dot solar cells. *Acc. Mater. Res.* **3**(8), 866–878 (2022). <https://doi.org/10.1021/accountsmr.2c00081>
14. Y. Han, W. Liang, X. Lin, Y. Li, F. Sun et al., Lattice distortion inducing exciton splitting and coherent quantum beating in CsPbI<sub>3</sub> perovskite quantum dots. *Nat. Mater.* **21**(11), 1282–1289 (2022). <https://doi.org/10.1038/s41563-022-01349-4>
15. H. Zhu, Y. Pan, C. Peng, H. Lian, J. Lin, 4-bromo-butyric acid-assisted in situ passivation strategy for superstable all-inorganic halide perovskite CsPbI<sub>3</sub> quantum dots in polar media. *Angew. Chem. Int. Ed.* **61**(22), e202116702 (2022). <https://doi.org/10.1002/anie.202116702>
16. S. Kumar, J. Jagielski, T. Marcato, S.F. Solari, C.J. Shih, Understanding the ligand effects on photophysical, optical, and electroluminescent characteristics of hybrid lead halide perovskite nanocrystal solids. *J. Phys. Chem. Lett.* **10**(24), 7560–7567 (2019). <https://doi.org/10.1021/acs.jpclett.9b02950>
17. M.A. Boles, D. Ling, T. Hyeon, D.V. Talapin, The surface science of nanocrystals. *Nat. Mater.* **15**(3), 364 (2016). <https://doi.org/10.1038/nmat4578>
18. D. Jia, J. Chen, R. Zhuang, Y. Hua, X. Zhang, Inhibiting lattice distortion of CsPbI<sub>3</sub> perovskite quantum dots for solar cells with efficiency over 16.6%. *Energy Environ. Sci.* **15**(10), 4201–4212 (2022). <https://doi.org/10.1039/d2ee02164a>
19. X. Ling, S. Zhou, J. Yuan, J. Shi, Y. Qian et al., 14.1% CsPbI<sub>3</sub> perovskite quantum dot solar cells via cesium cation passivation. *Adv. Energy Mater.* **9**(28), 19007 (2019). <https://doi.org/10.1002/aenm.201900721>
20. D. Jia, J. Chen, J. Qiu, H. Ma, M. Yu et al., Tailoring solvent-mediated ligand exchange for CsPbI<sub>3</sub> perovskite quantum dot solar cells with efficiency exceeding 16.5%. *Joule* **6**(7), 1632–1653 (2022). <https://doi.org/10.1016/j.joule.2022.05.007>
21. L.M. Wheeler, E.M. Sanehira, A.R. Marshall, P. Schulz, M. Suri et al., Targeted ligand-exchange chemistry on cesium lead halide perovskite quantum dots for high-efficiency photovoltaics. *J. Am. Chem. Soc.* **140**(33), 10504–10513 (2018). <https://doi.org/10.1021/jacs.8b04984>
22. L.N. Quan, D. Ma, Y. Zhao, O. Voznyy, H. Yuan et al., Edge stabilization in reduced-dimensional perovskites. *Nat. Commun.* **11**(1), 170 (2020). <https://doi.org/10.1038/s41467-019-13944-2>
23. X. Ling, J. Yuan, X. Zhang, Y. Qian, S.M. Zakeeruddin et al., Guanidinium-assisted surface matrix engineering for highly efficient perovskite quantum dot photovoltaics. *Adv. Mater.* **32**(26), e2001906 (2020). <https://doi.org/10.1002/adma.20201906>
24. J.X. Chen, D.L. Jia, E.M.J. Johansson, A. Hagfeldt, X.L. Zhang, Emerging perovskite quantum dot solar cells: feasible approaches to boost performance. *Energy Environ. Sci.* **14**(1), 224–261 (2021). <https://doi.org/10.1039/d0ee02900a>
25. A.H. Ip, S.M. Thon, S. Hoogland, O. Voznyy, D. Zhitomirsky et al., Hybrid passivated colloidal quantum dot solids. *Nat. Nanotechnol.* **7**(9), 577–582 (2012). <https://doi.org/10.1038/nnano.2012.127>
26. J. Shi, F. Li, Y. Jin, C. Liu, B. Cohen-Kleinstejn et al., In situ ligand bonding management of CsPbI(3) perovskite quantum dots enables high-performance photovoltaics and red light-emitting diodes. *Angew. Chem. Int. Ed.* **59**(49), 22230–22237 (2020). <https://doi.org/10.1002/anie.202010440>
27. M.T. Hoang, A.S. Pannu, Y. Yang, S. Madani, P. Shaw et al., Surface treatment of inorganic CsPbI(3) nanocrystals with guanidinium iodide for efficient perovskite light-emitting diodes with high brightness. *Nano-Micro Lett.* **14**(1), 69 (2022). <https://doi.org/10.1007/s40820-022-00813-9>
28. Y. Qian, Y. Shi, G. Shi, G. Shi, X. Zhang et al., The impact of precursor ratio on the synthetic production, surface chemistry, and photovoltaic performance of CsPbI<sub>3</sub> perovskite quantum dots. *Sol. RRL* **5**(5), 2100090 (2021). <https://doi.org/10.1002/solr.202100090>
29. F. Liu, C. Ding, Y. Zhang, T. Kamisaka, Q. Zhao et al., GeI<sub>2</sub> additive for high optoelectronic quality CsPbI<sub>3</sub> quantum dots and their application in photovoltaic devices. *Chem. Mater.* **31**(3), 798–807 (2019). <https://doi.org/10.1021/acs.chemmater.8b03871>
30. X. Lu, D. Yan, J. Feng, M. Li, B. Hou et al., Ecotoxicity and sustainability of emerging pb-based photovoltaics. *Sol. RRL* **6**(12), 2200699 (2022). <https://doi.org/10.1002/solr.20220699>
31. Q. Tian, G.Z. Ding, Y.T. Cai, Z.C. Li, X.Y. Tang et al., Enhanced performance of perovskite solar cells loaded with iodine-rich CsPbI<sub>3</sub> quantum dots. *ACS Appl. Energy Mater.* **4**(8), 7535–7543 (2021). <https://doi.org/10.1021/acsaem.1c00517>



32. X. Shen, Y. Zhang, S.V. Kershaw, T. Li, C. Wang et al., Zn-alloyed CsPbI<sub>3</sub> nanocrystals for highly efficient perovskite light-emitting devices. *Nano Lett.* **19**(3), 1552–1559 (2019). <https://doi.org/10.1021/acs.nanolett.8b04339>
33. Y.H. Huang, W.L. Luan, M.K. Liu, L. Turyanska, Ddab-assisted synthesis of iodine-rich CsPbI<sub>3</sub> perovskite nanocrystals with improved stability in multiple environments. *J. Mater. Chem. C* **8**(7), 2381–2387 (2020). <https://doi.org/10.1039/c9tc06566k>
34. J. Yuan, X. Ling, D. Yang, F. Li, S. Zhou et al., Band-aligned polymeric hole transport materials for extremely low energy loss  $\alpha$ -CsPbI<sub>3</sub> perovskite nanocrystal solar cells. *Joule* **2**(11), 2450–2463 (2018). <https://doi.org/10.1016/j.joule.2018.08.011>
35. L. Protesescu, S. Yakunin, M.I. Bodnarchuk, F. Krieg, R. Caputo et al., Nanocrystals of cesium lead halide perovskites (CsPbX<sub>3</sub>, X = Cl, Br, and I): Novel optoelectronic materials showing bright emission with wide color gamut. *Nano Lett.* **15**(6), 3692–3696 (2015). <https://doi.org/10.1021/nl5048779>
36. Z. Zhang, J. Sung, D.T.W. Toolan, S. Han, R. Pandya et al., Ultrafast exciton transport at early times in quantum dot solids. *Nat. Mater.* **21**(5), 533–539 (2022). <https://doi.org/10.1038/s41563-022-01204-6>
37. M. Liu, O. Voznyy, R. Sabatini, F.P. Garcia de Arquer, R. Munir et al., Hybrid organic-inorganic inks flatten the energy landscape in colloidal quantum dot solids. *Nat. Mater.* **16**(2), 258–263 (2017). <https://doi.org/10.1038/nmat4800>
38. M. Liu, S.D. Verma, Z. Zhang, J. Sung, A. Rao, Nonequilibrium carrier transport in quantum dot heterostructures. *Nano Lett.* **21**(21), 8945–8951 (2021). <https://doi.org/10.1021/acs.nanolett.1c01892>
39. Y. Zhang, G. Wu, F. Liu, C. Ding, Z. Zou et al., Photoexcited carrier dynamics in colloidal quantum dot solar cells: insights into individual quantum dots, quantum dot solid films and devices. *Chem. Soc. Rev.* **49**(1), 49–84 (2020). <https://doi.org/10.1039/c9cs00560a>
40. K. Chen, Q. Zhong, W. Chen, B. Sang, Y. Wang et al., Short-chain ligand-passivated stable  $\alpha$ -CsPbI<sub>3</sub> quantum dot for all-inorganic perovskite solar cells. *Adv. Funct. Mater.* **29**(24), 1900991 (2019). <https://doi.org/10.1002/adfm.201900991>
41. S. Lim, G. Lee, S. Han, J. Kim, S. Yun et al., Monodisperse perovskite colloidal quantum dots enable high-efficiency photovoltaics. *ACS Energy Lett.* **6**(6), 2229–2237 (2021). <https://doi.org/10.1021/acsenerylett.1c00462>
42. Z. Ding, S. Li, Y. Jiang, D. Wang, M. Yuan, Open-circuit voltage loss in perovskite quantum dot solar cells. *Nanoscale* **15**(8), 3713–3729 (2023). <https://doi.org/10.1039/d2nr06976h>
43. A. Ghorai, S. Mahato, S.K. Srivastava, S.K. Ray, Atomic insights of stable, monodispersed CsPbI<sub>3-x</sub>Br<sub>x</sub> (x = 0, 1, 2, 3) nanocrystals synthesized by modified ligand cell. *Adv. Funct. Mater.* **32**(32), 2202087 (2022). <https://doi.org/10.1002/adfm.202202087>
44. X. Huang, J. Hu, C. Bi, J. Yuan, Y. Lu et al., B-site doping of CsPbI<sub>3</sub> quantum dot to stabilize the cubic structure for high-efficiency solar cells. *Chem. Eng. J.* **421**, 127822 (2021). <https://doi.org/10.1016/j.cej.2020.127822>
45. Y. Zhou, H. Sternlicht, N.P. Padture, Transmission electron microscopy of halide perovskite materials and devices. *Joule* **3**(3), 641–661 (2019). <https://doi.org/10.1016/j.joule.2018.12.011>
46. Y. Li, J. Shi, J. Zheng, J. Bing, J. Yuan et al., Acetic acid assisted crystallization strategy for high efficiency and long-term stable perovskite solar cell. *Adv. Sci.* **7**(5), 1903368 (2020). <https://doi.org/10.1002/advs.201903368>
47. X. Ling, H. Zhu, W. Xu, C. Liu, L. Pan et al., Combined precursor engineering and grain anchoring leading to ma-free, phase-pure, and stable  $\alpha$ -formamidinium lead iodide perovskites for efficient solar cells. *Angew. Chem. Int. Ed.* **133**(52), 27505–27512 (2021). <https://doi.org/10.1002/ange.202112555>
48. S. Bi, H. Wang, J. Zhou, S. You, Y. Zhang et al., Halogen bonding reduces intrinsic traps and enhances charge mobilities in halide perovskite solar cells. *J. Mater. Chem. A* **7**(12), 6840–6848 (2019). <https://doi.org/10.1039/c8ta11835c>
49. E. Radicchi, E. Mosconi, F. Elisei, F. Nunzi, F. De Angelis, Understanding the solution chemistry of lead halide perovskites precursors. *ACS Appl. Energy Mater.* **2**(5), 3400–3409 (2019). <https://doi.org/10.1021/acsaem.9b00206>
50. F. Wang, M. Yang, S. Yang, X. Qu, L. Yang et al., Iodine-assisted antisolvent engineering for stable perovskite solar cells with efficiency >21.3%. *Nano Energy* **67**, 1042 (2020). <https://doi.org/10.1016/j.nanoen.2019.104224>
51. X. Zhang, H. Huang, X. Ling, J. Sun, X. Jiang et al., Homo-junction perovskite quantum dot solar cells with over 1 microm-thick photoactive layer. *Adv. Mater.* **34**(2), e2105977 (2022). <https://doi.org/10.1002/adma.202105977>
52. J. Shi, F. Li, C. Liu, X. Ling, X. Zhang et al., Inverted perovskite solar cells with >85% fill factor via sequential interfacial engineering. *Sol. RRL* **7**(11), 2300078 (2023). <https://doi.org/10.1002/solr.202300078>
53. O. Almora, M. Garcia-Batlle, G. Garcia-Belmonte, Utilization of temperature-sweeping capacitive techniques to evaluate band gap defect densities in photovoltaic perovskites. *J. Phys. Chem. Lett.* **10**(13), 3661–3669 (2019). <https://doi.org/10.1021/acs.jpcclett.9b00601>
54. X. Li, W. Zhang, X. Guo, C. Lu, J. Wei et al., Constructing heterojunctions by surface sulfidation for efficient inverted perovskite solar cells. *Science* **375**(6579), 434–437 (2022). <https://doi.org/10.1126/science.abl5676>
55. Z.Y. Ni, C.X. Bao, Y. Liu, Q. Jiang, W.Q. Wu et al., Resolving spatial and energetic distributions of trap states in metal halide perovskite solar cells. *Science* **367**(6484), 1352–1358 (2020). <https://doi.org/10.1126/science.aba0893>
56. D. Jia, J. Chen, X. Mei, W. Fan, S. Luo et al., Surface matrix curing of inorganic CsPbI<sub>3</sub> perovskite quantum dots for solar cells with efficiency over 16%. *Energy Environ. Sci.* **14**(8), 4599–4609 (2021). <https://doi.org/10.1039/d1ee01463c>